

# A Model of Surface Roughness Constitution in the Metal Cutting Process Applying Tools with Defined Stereometry

Stanisław Adamczak<sup>1,\*</sup> - Edward Miko<sup>1</sup> - Franci Čuš<sup>2</sup>

<sup>1</sup>Mechanical Engineering and Metrology Kielce, University of Technology, Kielce, Poland

<sup>2</sup>University of Maribor, Faculty of Mechanical Engineering, Maribor, Slovenia

*The process of surface roughness formation is complex and dependent on numerous factors. The analysis of the latest reports on the subject shows that mathematical relationships used for determining surface irregularities after turning and milling are not complete or accurate enough and, therefore, need to be corrected. A new generalized mathematical model of roughness formation was developed for surfaces shaped with round-nose tools. The model provides us with a quantitative analysis of the effects of the tool representation, undeformed chip thickness, tool vibrations in relation to the workpiece, tool run-out (for multicutter tools) and, indirectly, also tool wear. This model can be used to prepare separate models for most of the typical machining operations. Surface roughness is represented here by two parameters Ra and Rt. Simulations carried out for this model helped to develop nomograms which can be used for predicting and controlling the roughness Ra of surfaces sculptured by face milling.*

© 2009 Journal of Mechanical Engineering. All rights reserved.

**Keywords:** metal cutting, surface roughness finishing

## 0 INTRODUCTION

Machining is still the most commonly used method of product formation of all manufacturing technologies. As it is also very expensive, it seems reasonable to select the most suitable conditions. The research on the metal cutting process as a dimensional and surface treatment aims at improving the cutting efficiency and, consequently, the technical quality of the outer layer of a machine part [1] and [2].

Machining - a basic production operation - is predicted to improve or at least maintain its position in the engineering industry, especially if precision is involved [3].

The increasing accuracy of metal cutting, particularly turning and milling, causes that surfaces sculptured in this way seldom require finishing, which has a positive effect on the properties of ready products. If ceramic or CBN cutters are used it has become a rule to replace grinding with turning or milling after casting or forging so as to obtain required dimensions and surface finish [4]. Therefore, the geometrical structure generation and the properties of the outer layer obtained in the course of machining are important problems of both theoretical and experimental studies nowadays. Roughness is an

essential factor in tribology as it determines the quality of the outer layer and evaluates the cutting process [4].

Roughness, characterized by parameters determined by measuring its irregularities is said to be one of the most important factors affecting the operating properties of machine elements, expressed, among others, by friction conditions on contact surfaces, contact stresses, fatigue strength, corrosion resistance, tightness of joints, conditions of flow for fluids and gases, electrical and thermal contact resistance, superficial thermal radiation or magnetic properties [5].

The metal cutting process is generally accompanied by vibrations. These are mainly due to changeable forces produced by the tool, unbalance of rotating masses, performance of bearings, shafts, and toothed wheels, nonhomogeneity of the stock, etc. [4] and [6] to [8].

In the turning and milling operations, roughness is mainly a result of the stereometric and kinematical tool representation; also it is dependent on the unremoved fragment of the material, relative tool-workpiece vibrations, the tool run-out, and, finally, the tool wear [9].

The mathematical models discussed in specialized literature focus on the quantitative

\*Corr. Author's Address: Mechanical Engineering and Metrology Kielce University of Technology, Aleja Tysiąclecia Państwa Polskiego 7, 25-314 Kielce, Poland, adamczak@tu.kielce.pl

influence of tool representation, and on one of the following factors: vibrations, cutter run-out, and sometimes tool wear.

Since roughness constitution is reported to be an extremely significant process, a number of researchers are involved in the study of the effects of the above mentioned factors on surface roughness in the metal cutting process. Their results as well as those obtained by the authors were used to develop a new model of surface roughness constitution [15] to [18].

## 1 MODEL OF SURFACE ROUGHNESS IN METAL CUTTING

### 1.1 Model Assumptions

In practice, a cutting edge is never ideally sharp, thus a certain rounded cutting edge radius  $r_n$  needs to be taken into account. During a metal cutting process, part of the allowance is removed, its thickness being greater than a certain threshold thickness called minimum undeformed chip thickness  $h_{min}$  [3] and [9] to [11]. Generally, the process of metal removal is accompanied by relative tool-workpiece system vibrations that will be represented on the generated surface. It is crucial that the process of constitution of lateral roughness (in the feed direction) represented by the parameters  $Ra$  and  $Rt$  be modeled for surfaces sculptured with a rounded cutting edge described by the equivalent radius  $r_z$ .

The model includes:

- the stereometric-kinematic representation of the cutting edges,
- the unremoved fragment of the material,
- relative displacements of the tool and the stock in the direction normal to the machined surface,
- the tool run-out in the direction normal to the machined surface and
- the tool wear.

Moreover, it was assumed that:

- the vibrations in the machining system occur irrespective of the tool run-out;
- the stock material is ideally elastic;
- the influence of other factors disturbing the ideal representation of the tool is negligible;
- the tool wear affecting the roughness of machined surfaces results in a change in

the rounded cutting edge radius  $r_n$ ; this has an influence on the minimum undeformed chip thickness  $h_{min}$  and variations in relative displacements in the tool-workpiece (T-W) system [9].

### 1.2 Description of a Modeled Work Surface Profile

Fig. 1 shows the lateral profile of a surface generated after a pass of the  $i$ -th cutter during the  $l$ -th revolution of a multicutter tool moving along the  $x$ -axis with a feed motion, performing vibrations and showing cutter run-outs.

A lateral profile of such a surface is described by the following relationship:

$$y_{i_l}(x) = \frac{1}{2r_z} (x - f_z \cdot i_l)^2 + \rho_i + \xi_{i_l} \quad (1)$$

for the range  $b_{i_l} < x \leq b_{i_l+1}$  (Fig. 1) while:

$i_l = z(l - 1) + i - 1$  where:  $r_z$  – equivalent radius,  $f_z$  – feed per tooth  $\rho_i$  – instantaneous orientation of the  $i$ -th cutter in relation to the workpiece resulting from the face run-out,  $\xi_{i_l}$  – instantaneous relative displacement of the  $i$ -th cutter during the  $l$ -th revolution of a multicutter tool due to vibrations,  $z$  – number of cutters in the multicutter tool.

The instantaneous orientation of the  $i$ -th cutter in relation to the workpiece due to the face run-out  $\rho_i$  can be described using the relationship:

$$\rho_i \approx -e \cdot \cos \left[ (i-1) \cdot \frac{2\pi}{z} \right] \quad (2)$$

where:  $e$  face run-out of the cutters. The range limits are given by:

$$b_{i_l} = f_z \cdot \left( i_l - \frac{1}{2} \right) + \frac{r_z}{f_z} \cdot (\rho_i - \rho_{i-1} + \xi_{i_l} - \xi_{i_l-1} + h_{min}) \quad (3)$$

$$b_{i_l+1} = f_z \cdot \left( i_l + \frac{1}{2} \right) + \frac{r_z}{f_z} \cdot (\rho_{i+1} - \rho_i + \xi_{i_l+1} - \xi_{i_l} + h_{min}) \quad (4)$$

where:  $h_{min}$  – minimum undeformed chip thickness.

$\xi_{i_l}$  was assumed to be a sequence of independent random variables with uniform.

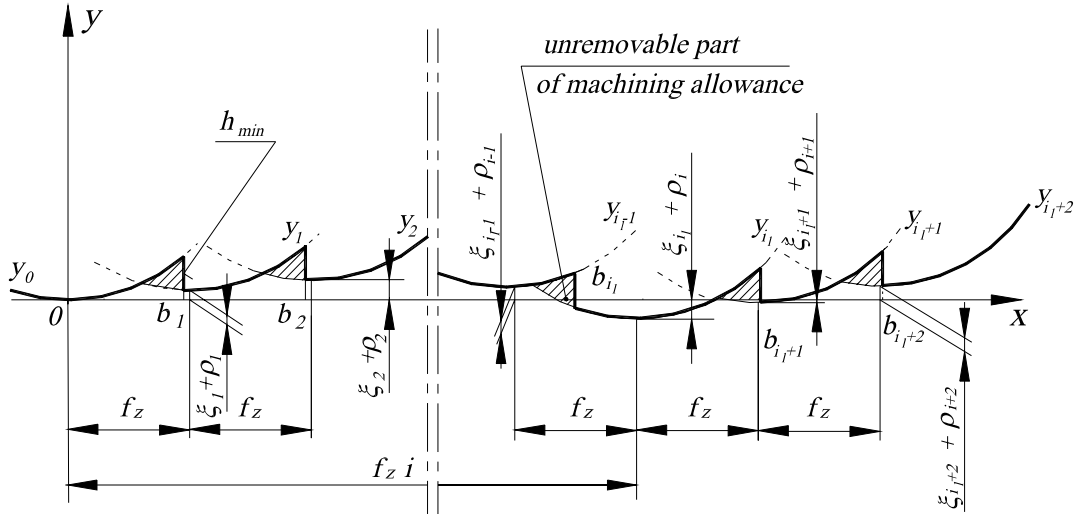


Fig. 1. Lateral roughness profile of a surface face-milled with the feed rate  $f_z$  with a milling head equipped with round corner cutters with the radius  $r_c$  due to relative displacements of the tool and the workpiece  $\xi_{i_i}$  and an instantaneous cutter position resulting from the face run-out  $\rho_i$

distribution of probability where the mean value equals 0 and the variance is  $D^2(\xi)$ . When  $\xi_{i_i}$  are independent random variables, then the profile of a modeled surface is no longer a periodic curve; it is said to be a stochastic process algebra.

To determine the parameter  $Ra$  of a surface described by Eq. 1, it is necessary to define a functional for a set of the stochastic process algebras.

The arithmetic mean profile deviation (given by the function  $y(x)$ ) from the mean line position  $\bar{y}$  at the elementary length  $l_e$  is determined from the relationship:

$$Ra = \frac{1}{l_e} \int_0^{l_e} |y(x) - \bar{y}| dx. \tag{5}$$

Then, the position of the mean line is established from the following equation:

$$\bar{y} = \frac{1}{l_e} \int_0^{l_e} y(x) dx. \tag{6}$$

Squaring both sides of relationship (5) and applying Schwarz inequality, it is possible to determine the parameter  $Ra$  of the modeled surface. Then, we get:

$$Ra^2 = \left[ \frac{1}{l_e} \int_0^{l_e} |y(x) - \bar{y}| dx \right]^2 \leq \frac{1}{l_e} \int_0^{l_e} [y(x) - \bar{y}]^2 dx = \frac{1}{l_e} \int_0^{l_e} [y(x)]^2 dx - \frac{2}{l_e} \bar{y} \int_0^{l_e} y(x) dx + \frac{1}{l_e} \bar{y}^2 \int_0^{l_e} dx \tag{7}$$

and after transition to the limit with  $l_e \rightarrow \infty$ :

$$Ra^2 \leq [y^2 - \bar{y}^2]. \tag{8}$$

This inequality can be transformed into the following equality:

$$Ra = \theta \sqrt{[y^2 - \bar{y}^2]} \quad \text{for } \theta \in (0, 1) \tag{9}$$

where:  $\theta$  – form factor of the modeled profile.

### 1.3 Determining the Parameter $Ra$ of the Modeled Profile for High Feed Rates

$$f_z > \sqrt{2r_z h_{\min}}$$

In order to derive the equation to be used for determining the parameter  $Ra$ , it is required to establish the quantities  $\bar{y}$  and  $y^2$ :

$$\bar{y} = \lim_{l_c \rightarrow \infty} \frac{1}{l_c} \int_0^{l_c} [y(x)] dx = \lim_{n \rightarrow \infty} \frac{1}{n \cdot f_z \cdot z} \cdot \sum_{i_1=0}^n \int_{b_{i_1}}^{b_{i_1+k}} \left[ \frac{1}{2r_z} (x - f_z \cdot i_1)^2 + \rho_i + \xi_{i_1} \right] dx \quad (10)$$

$$\overline{y^2} = \lim_{l_c \rightarrow \infty} \frac{1}{l_c} \int_0^{l_c} [y(x)]^2 dx = \lim_{n \rightarrow \infty} \frac{1}{n \cdot f_z \cdot z} \cdot \sum_{i_1=0}^n \int_{b_{i_1}}^{b_{i_1+k}} \left[ \frac{1}{2r_z} (x - f_z \cdot i_1)^2 + \rho_i + \xi_{i_1} \right]^2 dx \quad (11)$$

Substituting the integration limits (3) and (4) into (10) and (11) and performing calculations while neglecting moments of the variables  $\xi_{i_1}$ , an order higher than the second one as well as the power of these moments and the sum of the variables  $\rho_i$  in even powers, higher than the second as low values of a higher order, we got:

$$\bar{y} = \frac{f_z^2}{24r_z} + \frac{r_z h_{\min}^2}{2f_z^2} - \frac{r_z}{f_z^2} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right] \quad (12)$$

$$\overline{y^2} = \frac{f_z^4}{320r_z^2} + \frac{h_{\min}^2}{8} + \frac{r_z^2 h_{\min}^4}{4f_z^4} + 3 \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{3} \cos \frac{2\pi}{z} \right) \right] + \frac{r_z^2 h_{\min}^2}{f_z^4} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right]. \quad (13)$$

Performing transformations and calculations, we obtain:

$$Ra = \left\{ \frac{f_z^4}{972r_z^2} + \frac{5}{8l} h_{\min}^2 + \frac{50}{8l} \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right] + \frac{40r_z^2 h_{\min}^2}{27f_z^4} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right] \right\}^{\frac{1}{2}}. \quad (14)$$

This is an equation relevant for  $f_z > \sqrt{2r_z h_{\min}}$ .

#### 1.4 Determining the Parameter $Ra$ for the Feed Rates $f_z \leq \sqrt{2r_z h_{\min}}$

A general relationship will be applied to calculate the parameter  $Ra$  for  $\sqrt{r_z h_{\min}} < f_z \leq \sqrt{2r_z h_{\min}}$ , as well as for the case of  $f_z \leq \sqrt{r_z h_{\min}}$ , i.e. when part of the material is removed with the  $k$ -th cutter of the multicutter tool. A profile obtained by cutting with small feed rates when the area of unremoved material is partly smoothed with the  $k$ -th cutter is shown in Fig. 2.

The equation of the  $i$ -th parabola is given by relationship (1), while the equation of the  $(i + k)$ -th parabola is written in the following form:

$$y_{i+k} = \frac{1}{2r_z} [x - f_z (i + k)]^2 + \rho_{i+k} + \xi_{i+k}. \quad (15)$$

The position of point  $b_{i+k}$  (Fig. 2) was determined from:

$$y_{i_1} (b_{i_1+k}) - h_{\min} = y_{i_1+k} (b_{i_1+k}) \quad (16)$$

Substituting relationships (1) and (15) into (16) and performing certain transformations gives:

$$b_{i_1+k} = f_z \left( i_1 + \frac{k}{2} \right) + \frac{r_z}{k \cdot f_z} \left( \rho_{i_1+k} - \rho_{i_1} + \xi_{i_1+k} - \xi_{i_1} + h_{\min} \right) \quad (17)$$

Similarly, the parameter  $Ra$  of the modeled surface can be calculated using the values of  $\bar{y}$  and  $\overline{y^2}$ :

$$\bar{y} = \lim_{l_c \rightarrow \infty} \frac{1}{l_c} \int_0^{l_c} [y(x)] dx = \lim_{n \rightarrow \infty} \frac{l}{n \left( \frac{f_z \cdot k}{2} + \frac{r_z h_{\min}}{k \cdot f_z} \right) z} \cdot \sum_{i_1=0}^n \int_{f_z i_1}^{b_{i_1+k}} \left[ \frac{1}{2r_z} (x - f_z \cdot i_1)^2 + \rho_i + \xi_{i_1} \right] dx \quad (18)$$

$$\overline{y^2} = \lim_{l_c \rightarrow \infty} \frac{1}{l_c} \int_0^{l_c} [y(x)]^2 dx = \lim_{n \rightarrow \infty} \frac{1}{n \left( \frac{f_z \cdot k}{2} + \frac{r_z h_{\min}}{k \cdot f_z} \right) z} \cdot \sum_{i_1=0}^n \int_{f_z i_1}^{b_{i_1+k}} \left[ \frac{1}{2r_z} (x - f_z \cdot i_1)^2 + \rho_i + \xi_{i_1} \right]^2 dx \quad (19)$$

Integrating, transforming, and neglecting low values of a higher order, we get:

$$\bar{y} = \frac{f_z^2 k^2}{24r_z} + \frac{r_z h_{\min}^2}{6f_z^2 k^2} + \frac{h_{\min}}{6} - \frac{r_z}{f_z^2 k^2} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right] + \frac{4r_z^2 h_{\min}}{f_z^2 k^2 (k^2 f_z^2 + 2r_z h_{\min})} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right] \quad (20)$$

$$\begin{aligned} \bar{y}^2 = & \frac{f_z^4 k^4}{320 r_z^2} + \frac{3}{40} h_{\min}^2 + \frac{f_z^2 k^2 h_{\min}}{40 r_z} + \\ & + \frac{r_z h_{\min}^3}{10 f_z^2 k^2} + \frac{r_z^2 h_{\min}^4}{20 f_z^4 k^4} + \frac{3}{4} D^2(\xi) \left[ 1 + \frac{4 r_z^2 h_{\min}^2}{3 f_z^4 k^4} \right] + \\ & + \frac{3}{4} D^2(\rho) \left[ 1 + \frac{4}{3} \left( \frac{r_z^2 h_{\min}^2}{f_z^4 k^4} + 4 \cos \frac{2\pi}{z} \frac{r_z^2 h_{\min}^2}{f_z^4 k^4} \cos \frac{2\pi}{z} \right) \right]. \end{aligned} \quad (21)$$

After the necessary transformations and calculations, it yields:

$$\begin{aligned} Ra = & \left\{ \frac{f_z^2 k^2}{18 \sqrt{3} r_z} + \frac{2 h_{\min}}{9 \sqrt{3}} \left( 1 + \frac{r_z h_{\min}}{f_z^2 k^2} \right) \right\}^2 + \\ & + \frac{50}{81} \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right] + \\ & + \frac{40}{81} \left[ \frac{r_z^2 h_{\min}^2}{f_z^2 k^2 (f_z^2 k^2 + 2 r_z h_{\min})} + \frac{2 r_z^3 h_{\min}^3}{f_z^4 k^4 (f_z^2 k^2 + 2 r_z h_{\min})} \right] \cdot \\ & \cdot \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right]^{\frac{1}{2}}. \end{aligned} \quad (22)$$

The relationship can be applied when the feed rate  $f_z$  ranges:

$$\sqrt{\frac{2}{(k+1)k} r_z h_{\min}} < f_z \leq \sqrt{\frac{2}{(k-1)k} r_z h_{\min}} \quad \text{for } k = 2, 3, 4, \dots$$

When no smoothing is required, and the area of unremoved material sculptured with subsequent cutters does not decrease, then  $k = 1$  is substituted into (22). As a result we get:

$$\begin{aligned} Ra = & \left\{ \left[ \frac{f_z^2}{18 \sqrt{3} r_z} + \frac{2 h_{\min}}{9 \sqrt{3}} \left( 1 + \frac{r_z h_{\min}}{f_z^2} \right) \right]^2 + \right. \\ & + \frac{50}{81} \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right] + \\ & \left. + \frac{40}{81} \left[ \frac{r_z^2 h_{\min}^2}{f_z^2 (f_z^2 + 2 r_z h_{\min})} + \frac{2 r_z^3 h_{\min}^3}{f_z^4 (f_z^2 + 2 r_z h_{\min})} \right] \right\}^{\frac{1}{2}} \cdot \\ & \cdot \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right] \end{aligned} \quad (23)$$

The relationship is relevant for the following feed rate:  $\sqrt{r_z h_{\min}} \leq f_z \leq \sqrt{2 r_z h_{\min}}$ .

### 1.5 Model Analysis

Depending on the profile form, which results from the feed rate, several characteristic

equations were derived. The relationships used for determining the parameter  $Ra$  of machined surfaces for the particular ranges of feed rates are given in (14), (22) and (23).

Experiments have shown that when turning and milling with cutters characterized by various levels of wear  $VB_c$ , the rounded cutting edge radius  $r_n$  rose, and so did the amplitude and variance ( $D^2(\xi)$ ) of relative T-W system vibrations, and this, accordingly, caused an increase in the roughness of surface. The wear of cutters leads to an increase in the rounded cutting edge and, consequently, to a rise in the cutting forces, which cause a growth in the amplitude of relative T-W system vibrations [12] and [13].

In a cutting process when feed rates are high  $f_z > \sqrt{2 r_z h_{\min}}$ , the member containing the feed  $\left( \frac{f_z^4}{972 r_z^2} \right)$  plays an important role, as it includes the influence of the cutter representation (14).

It has been revealed that in such a case the effects of the stereometric - kinematic representation of cutters on the value of the parameter  $Ra$  is increasingly big. With an increasing feed rate, the influence of the cutter representation decreases (the member containing the feed decreases), and the members containing  $h_{\min}$  and  $D^2(\xi)$  and  $D^2(\rho)$  of (23) begin to play a significant role.

Of importance is case 3 (22) occurring in cutting with small feed rates, i.e.  $f_z \leq \sqrt{r_z h_{\min}}$ . A series of equations relevant for the particular ranges of feed were derived for this case This infinite series of equations was written with the aid of one recurrent relationship. In this case, during machining with small feed rates, some of the marks of unevenness left by the  $k$ -th cutter are smoothed. (22) and (23) are complex and therefore inconvenient and impractical. Thus, it was necessary to substitute them with a simpler relationship shown in Table 1. The error resulting from this approximation in a most unfavorable theoretical case does not exceed 15%. However, for conditions of an after-machining process, it will range 1 to 5%, which is permissible [9]. From the simplified relationship it follows that for  $f_z \leq \sqrt{2 r_z h_{\min}}$  the feed rate does not affect surface roughness considerably.

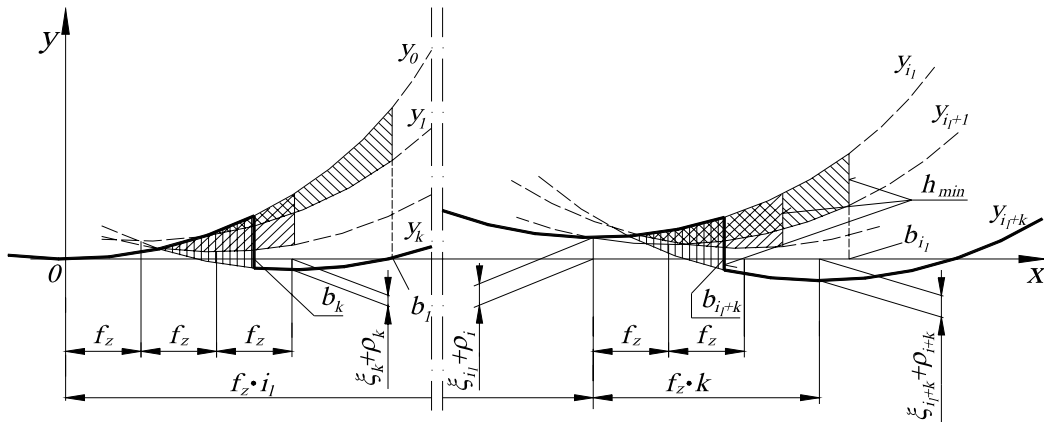


Fig. 2. Lateral roughness profile of a surface face-milled with a low feed rate  $f_z$  using round corner cutters with the radius  $r_s$ , due to relative displacements  $\xi_{i_j}$  of the tool and the workpiece and an instantaneous position of cutters due to a face run-out

In practice, reducing the feed rate below the above mentioned value is not recommended, as it does not lead to a decrease in surface roughness, and for  $f_z \leq 100 \frac{e}{z}$  it may even cause its increase. It can be explained by the fact that for small feed rates  $f_z \leq 100 \frac{e}{z}$ , the face run-out previously resulting in surface waviness will now cause and increase surface roughness. To decrease roughness, it is necessary to reduce  $h_{min}$  and  $D(\xi)$ .

By applying sharp cutters with a minimum rounded cutting edge radius  $r_n$ , we are able to reduce the minimum undeformed chip thickness  $h_{min}$ . It is undesirable to use such cutters intensively as this may lead to considerable wear.

The standard deviation of relative displacements  $D(\xi)$  can be reduced by decreasing the amplitude of relative displacements  $A_\xi$ , which makes the machining system more rigid and causes the attenuation of vibrations acting on the system. Moreover, it is crucial that the machining conditions be selected properly avoiding the occurrence of self-excited vibrations.

Similarly, applying the definition, we could establish the total height of the roughness profile  $Rt$ . The relationships shown in Table 2 were used to calculate  $Rt$  as well as  $Ra$ .

The generalized model can be used to develop individual models for each cutting

operation. When surfaces are machined with a single-cutter tool, then in formula (14), (22) and (23) as well as in the above tables, the members describing the influence of the run-out can be eliminated assuming that  $D2(\rho) = 0$ .

Then, depending on the type of machining the equivalent radius  $r_z$  should be replaced with a suitable quantity. Thus, for example, for straight turning or facing as well as face milling with a rounded corner tool, we have  $r_z = r_s$ . It can be used also to forecast and control surface roughness in planing and chiseling, provided we employ tools with a rounded cutting edge having the radius  $r_s$ . This model of surface roughness constitution can be applied also in the operations of milling, turning, drilling, reaming, and counterboring of a cylindrical surface (with the counterbore circumference).

For oblique turning, the formula should include the equivalent radius  $r_z$  described by relationship [9]:

$$r_z = \frac{(D - 2a_p) \cos^2 \kappa_r}{2(\tan^2 \lambda_s + \sin^2 \kappa_r)} \tag{24}$$

where:  $D$  – diameter of the workpiece,

$a_p$  – depth of cut,

$\kappa_r$  – tool cutting edge angle,

$\lambda_s$  – cutting edge inclination.

For a cylindrical milling operation, we should assume that  $r_z = d/2$ .

All in all, the developed models seem to be applicable in most sculpturing and finishing processes if tools with specified stereometry of cutters are used.

## 2 FORECASTING THE PARAMETER Ra FOR FACE MILLING WITH SPHERICAL

The profile of a surface generated after a pass of the  $i$ -th cutter ( $i = 1, 2, 3, \dots, z$ ) during the  $l$ -th ( $l = 1, 2, 3, \dots, n$ ) revolution of the milling head moving along the  $x$ -axis with an assigned feed rate with relative vibrations and showing face run-out of cutters can be described applying the equation obtained by substituting  $r_z = d/2$  into (1):

$$y_{i_1}(x) = \frac{1}{d} \cdot (x - f_z \cdot i_1)^2 + \rho_i + \xi_{i_1} \quad (25)$$

where:  $d$  – diameter of cutters.

Fig. 3 presents a lateral surface profile taking into account the factors described in section 1.1 during a single revolution of a milling head equipped with spherical cutters [14].

The mean arithmetic deviation of the profile (given by the function  $y_{i_1}(x)$ ) from the mean line will be established from relationship (14) assuming that  $D^2(\rho) = 0$ :

$$Ra = \sqrt{\frac{f_z^4}{243d^2} + \frac{5}{81}h_{min}^2 + \frac{50}{81}D^2(\xi) + \frac{10d^2h_{min}^2}{27f_z^4}D^2(\xi)} \quad (26)$$

Taking into consideration the above factors, it is possible to determine the total thickness of the surface roughness profile  $Rt$  (Table 2):

$$Rt = \frac{f_z^2}{4d} + \frac{h_{min}}{2} \left( 1 + \frac{d \cdot h_{min}}{2f_z^2} \right) + 2A_\xi \quad (27)$$

Equations (26) and (27) are relevant for  $f_z > \sqrt{dh_{min}}$ . On the other hand, when feed rates per tooth range  $100 \frac{e}{z} \leq f_z \leq \sqrt{dh_{min}}$ , the value of the parameter  $Ra$  will be (Table 1).

Moreover,

$$Ra = \sqrt{\frac{16}{243}h_{min}^2 + \frac{60}{81}D^2(\xi)} \quad (28)$$

Accordingly, it is possible to determine the value of the parameter  $Rt$ :

$$Rt = \frac{f_z^2}{4d} + 2A_\xi + h_{min} \quad (29)$$

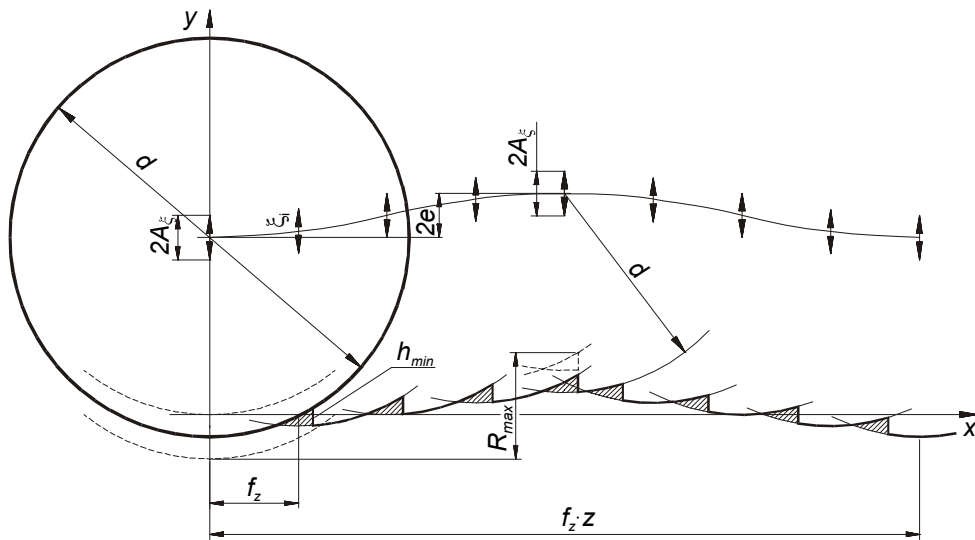


Fig. 3. Lateral microroughness profile of a surface face-milled with spherical tools with the diameter  $d$  applying the feed rate  $f_z$  due to relative vibrations of the tool and the workpiece  $\xi_{i_1}$  and an instantaneous cutter position owing to a face run-out  $\rho_i$  during one revolution

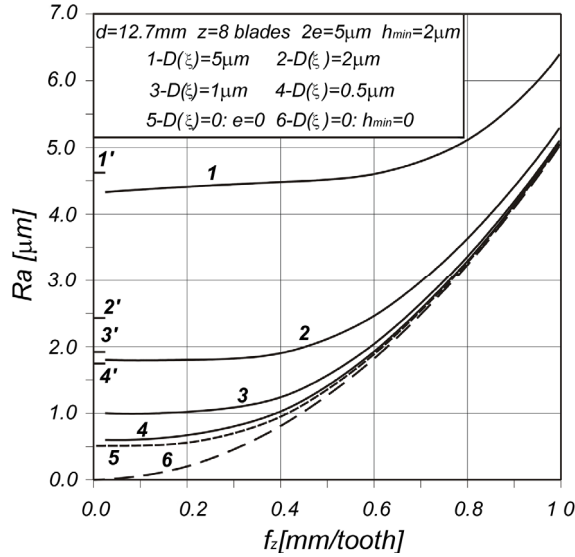


Fig. 4. Nomogram for forecasting the value of the roughness parameter  $Ra(f_z, D(\xi))$  for surfaces face-milled with rounded corner tools with the diameter  $d$

Table 1. Generalized approximate formula used for calculating the parameter  $Ra$  when applying tools with defined stereometry

Item	Feed range $f_z$	Approximate formula for calculating the parameter $Ra$
1.	$f_z > \sqrt{2r_z h_{min}}$	$Ra = \sqrt{\frac{f_z^4}{972r_z^2} + \frac{5}{81}h_{min}^2 + \frac{50}{81} \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right] + \frac{40r_z^2 h_{min}^2}{27f_z^4} \left[ D^2(\xi) + D^2(\rho) \left( 1 - \cos \frac{2\pi}{z} \right) \right]}$
2.	$100 \frac{e}{z} \leq f_z \leq \sqrt{2r_z h_{min}}$	$Ra = \sqrt{\frac{16}{243} h_{min}^2 + \frac{60}{81} D^2(\xi)}$
3.	$f_z \leq 100 \frac{e}{z}$	$Ra = \sqrt{\frac{16}{243} h_{min}^2 + \frac{60}{81} \left[ D^2(\xi) + D^2(\rho) \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right]}$

Table 2. Generalized formula used for calculating the parameter  $Rt$  when applying tools with defined stereometry

Item	Feed range $f_z$	Formula for calculating the parameter $Rt$	Approximate formula for calculating the parameter $Rt$
1.	$f_z > \sqrt{r_z h_{min}}$	$Rt = \frac{f_z^2}{8r_z} + \frac{h_{min}}{2} \left( 1 + \frac{r_z h_{min}}{f_z^2} \right) + 2A_\xi$	-----
2.	$\sqrt{\frac{2}{(k+1)k} r_z h_{min}} < f_z \leq \sqrt{\frac{2}{(k-1)k} r_z h_{min}}$ $k = 2, 3, 4, \dots$	a) $100 \frac{e}{z} < f_z \leq \sqrt{r_z h_{min}}$	$Rt = \frac{f_z^2 k^2}{8r_z} + \frac{h_{min}}{2} \left( 1 + \frac{r_z h_{min}}{f_z^2 k^2} \right) + 2A_\xi$  $Rt = h_{min} + 2A_\xi$
		b) $f_z \leq 100 \frac{e}{z}$	$Rt = \frac{f_z^2 k^2}{8r_z} + \frac{h_{min}}{2} \left( 1 + \frac{r_z h_{min}}{f_z^2 k^2} \right) + 2A_\xi + 2e$  $Rt = h_{min} + 2A_\xi + 2e$



When  $f_z \geq 100 \frac{e}{z}$ , the face run-out of cutters  $e$  results in surface waviness. For small feed rates, on the other hand, i.e. when  $f_z < 100 \frac{e}{z}$ , the run-out will cause roughness, thus, according to Table 1 and (28), we get respectively:

$$Ra = \sqrt{\frac{16}{243} h_{\min}^2 + \frac{60}{81} \left[ D^2(\xi) + \frac{e^2}{2} \cdot \left( 1 + \frac{1}{5} \cos \frac{2\pi}{z} \right) \right]}$$

$$Rt = h_{\min} + 2A_\xi + 2e \quad (31)$$

Basing on (26), (28) and (30), it was possible to develop a nomogram for forecasting the values of  $Ra$  in face milling with spherical cutters under conditions to be found in practice (Fig. 4)

Analyzing the curves in Fig. 4, we can see that the influence of the feed rate  $f_z$  on the value of the parameter  $Ra$  is more and more considerable when the relative vibrations  $D(\xi)$  decrease. The value of the parameter  $Ra$  decreases with the feed rate  $f_z$  but only to a certain limit dependent on the relative vibrations  $D(\xi)$  and the minimum deformed chip thickness  $h_{\min}$  (curves 1 to 4). For a small feed rate, i.e.

$f_z < 100 \frac{e}{z}$ , the roughness increases even in jumps; this is caused by the fact that for these feed rates the face run-out of the cutters  $e$  leads to the constitution of roughness containing microirregularities (curves 1' to 4').

### 3 CONCLUSIONS

1. The roughness of surfaces sculptured with multicutter tools, the cutters having specified stereometry is quantitatively affected by the cutting edge representation, the unremoved fragment of material, relative tool-workpiece system vibrations, the cutter run-out, and partly the tool wear.
2. There exists a general mathematical model for the constitution of surface roughness independent of the method of metal cutting using tools with specified geometry.
3. The vibrations of the tool-workpiece system, the cutter run-out (for milling), and the unremoved fragment of material constitute a

limitation for surface roughness, thus it is necessary to reduce them to a minimum.

4. The feed rate is reported to have a considerable influence on the roughness of surfaces in face-milling only for high feed rates per tooth and small radii of the cutters. The influence becomes greater with an increase in the feed rate and a decrease in relative displacements as well as the minimum deformed chip thickness. The feed rate from the range  $100 \frac{e}{z} \leq f_z \leq \sqrt{2r_z h_{\min}}$  does not affect surface roughness in face milling.
5. It is recommended that a face milling operation should be performed with feeds per tooth being in the upper limit of or even slightly above the  $100 \frac{e}{z} \leq f_z \leq \sqrt{2r_z h_{\min}}$  range; applying lower values, we will fail to decrease surface roughness (and the feed rates  $f_z < 100 \frac{e}{z}$  will even increase it), and reduce the process capacity.

### 4 NOMENCLATURE

- $A_\xi$  – amplitude of the tool-workpiece system vibrations,  $\mu\text{m}$
- $D^2(\xi)$  – variance of the tool-workpiece system vibrations,  $\text{pm}^2$
- $D^2(\rho)$  – variance of the multicutter tool run-out,  $\text{pm}^2$
- $D$  – workpiece diameter,  $\text{mm}$ ,  $\mu\text{m}$
- $d$  – milling head cutter diameter,  $\text{mm}$ ,  $\mu\text{m}$
- $h_{\min}$  – minimum undeformed chip thickness,  $\mu\text{m}$
- $e$  – face (radial) run-out of cutters,  $\mu\text{m}$
- $f$  – feed per revolution,  $\text{mm/rev}$ ,  $\mu\text{m/rev}$
- $f_z$  – feed per tooth,  $\text{mm/tooth}$ ,  $\mu\text{m/tooth}$
- $\kappa_r$  – tool major cutting edge angle,  $^\circ$
- $\xi_{i_1}$  – instantaneous relative displacement of the  $i$ -th cutter during the  $l$ -th revolution due to tool-workpiece vibrations,  $\mu\text{m}$
- $\rho_{i_1}$  – instantaneous position of the  $i$ -th cutter in relation to the workpiece due to cutter run-out,  $\mu\text{m}$
- $L$  – length of a measurement section,  $\text{mm}$
- $l_e$  – length of elementary measurement section,  $\text{mm}$

$Ra$	– arithmetic mean of roughness profile ordinates, $\mu\text{m}$
$Rt$	– total roughness profile height, $\mu\text{m}$
$r_\epsilon$	– corner radius, mm, $\mu\text{m}$
$r_n$	– rounded cutting edge radius, mm
$r_z$	– equivalent radius, mm, $\mu\text{m}$
$\lambda_s$	– tool cutting edge inclination, $^\circ$
$\bar{y}$	– mean value of the modeled profile, $\mu\text{m}$
$z$	– number of milling cutters or milling heads

## 5 REFERENCES

- [1] Żebrowski H. (1998) Constituting the outer layer in the turning process with increased cutting speeds, *Mechanik* no. 11, p. 686-692, (in Polish).
- [2] Peterka J. (2004) A New Approach to Calculating the Arithmetical Mean Deviation of a Profile during Copy Milling. *Journal of Mechanical Engineering*, vol. 50, no. 12, pp. 594-597.
- [3] Grzesik W. (1998) Fundamentals of metal cutting, Wydawnictwa Naukowo-Techniczne, Warszawa, (in Polish).
- [4] Jang D.Y., Choi Y.G., Kim H.G., Hsiao A. (1996) Study of the correlation between surface roughness and cutting vibrations to develop an on-line roughness measuring technique in hard turning. *International Journal of Machine Tools and Manufacture*, vol. 36, no. 4, p. 453-464.
- [5] Liubimov V., Oczóś K. (1997) Selected problems of surface roughness formation in machining processes, *Mechanik* no. 3, p. 81-84, (in Polish).
- [6] Lin, S.C., Chang M.F. (1998) A study on the effects of vibrations on the surface finish using a surface topography simulation model for turning. *International Journal of Machine Tools & Manufacture* no. 38, p. 763-782.
- [7] Lin, R., Koren Y. (1996) Efficient toolpath planning for machining freeform surfaces. *Transactions of the ASME, Journal of Manufacturing Science and Engineering*, vol. 118, p. 20-28.
- [8] Zhang G.M., Kapoor S.G. (1991) Dynamic generation of machined surface. Part 1: Description of a random excitation system. *Transactions of the ASME. Journal of Engineering for Industry*, vol. 113, p. 137-144.
- [9] Miko E. (2004) Determination of the microirregularities on metallic surfaces sculptured by cutting tools with defined stereometry, *Monografie, Studia, Rozprawy, Kielce*, no. 46, (in Polish).
- [10] Kawalec M. (1990) Machining of hardened steel and cast iron using tools with specified geometry of cutters. *Wydawnictwo Politechniki Poznańskiej, seria Rozprawy*, no. 234, Poznań, (in Polish).
- [11] Wawrzyniak W., Strelow B. (1980) Fine turning of materials with high hard cutting materials, *Feingerätetechnik*, vol. 29, no. 5, p. 208-210, (in German).
- [12] Bonifaćio M., Diniz A. E. (1994) Correlating tool wear, tool life, surface roughness and tool vibration in finish turning with coated carbide tools. *Wear*, vol. 173, p. 137-144.
- [13] Wilkinson P. et al. (1997) Surface finish parameters as diagnostics of tool wear in face milling. *Wear*, vol. 205, pp. 47-54.
- [14] Župerl U., Čuš F., Muršec B., Ploj A. (2004) A Hybrid analytical-neural network approach to the determination of optimal cutting conditions, *J. mater. process. technol.* 157/158, p. 82-90.
- [15] Kopač, J., Kržič, P. CAM algorithm as important element by achieving of good machined surface quality, *Journal of Mechanical Engineering* 2008, vol. 54, no. 4, p. 280-287.
- [16] Pušavec, F., Krajnik, P., Kopač, J. High-speed cutting of soft materials, *Journal of Mechanical Engineering*, 2006, vol. 52, no. 11, p. 706-722.
- [17] Balič, J., Klančnik, S., Brezovnik, S. Feature extraction from CAD model for milling strategy prediction, *Journal of Mechanical Engineering*, 2008, vol. 54, no. 5, p. 301-307.
- [18] Župerl, U., Čuš, F., Gečevska, V. Optimization of the characteristic parameters in milling using the PSO evolution technique, *Journal of Mechanical Engineering*, 2007, vol. 53, no. 6, p. 354-368.