

A CARBON-NANOTUBES COUNTER ELECTRODE FOR  
FLEXIBLE DYE-SENSITIZED SOLAR CELLSELEKTRODA IZ OGLJIKOVIH NANOCEVK ZA TANKOPLASTNE  
BARVNO OBČUTLJIVE SONČNE CELICE**Aleksandra Drygala<sup>1</sup>, Leszek Adam Dobrzański<sup>1</sup>, Marzena Prokopiuk vel  
Prokopowicz<sup>1</sup>, Marek Szindler<sup>1</sup>, Krzysztof Lukaszewicz<sup>1</sup>, Marian Domański<sup>2</sup>**<sup>1</sup>Institute of Engineering Materials and Biomaterials, Silesian University of Technology, Konarskiego St. 18a, 44-100, Gliwice, Poland<sup>2</sup>Centre of Polymer and Carbon Materials, Polish Academy of Sciences, M.Curie-Skłodowskiej St. 34, 41-819, Zabrze, Poland  
aleksandra.drygala@polsl.pl*Prejem rokopisa – received: 2016-07-15; sprejem za objavo – accepted for publication: 2017-01-20*

doi:10.17222/mit.2016.206

Dye-sensitized solar cells (DSSCs) are an attractive alternative to conventional crystalline silicon solar cells because of their low-cost, relatively high photon-to-current conversion efficiency for low energy consumption and simple fabrication process. The dye-sensitized solar cell consists of the following components: a photoanode, a dye, an electrolyte, and a counter electrode. The counter electrode is a crucial element, in which the triiodide is reduced to iodide by electrons flowing through the external circuit. Platinum is the most used material for a counter electrode in DSSCs, due to its electrocatalytic activity towards  $I_3^-$  reduction. However, the use of platinum may not be a suitable option because of its high cost. Additionally, to achieve widespread application of next-generation photovoltaics, it is important to develop flexible devices. Given this, the paper presents the influence of mechanical stress arising from the bending of a flexible substrate on the morphology, the resistance of counter electrode based on carbon nanotubes as well as the electrical properties of dye-sensitized solar cells.

Keywords: photovoltaics, dye-sensitized solar cells, flexible substrates, counter electrode, carbon nanotubes

Fleksibilne tankoslojne barvno občutljive sončne celice (angl. DSSCs) so privlačna alternativa konvencionalnim kristalnim silicijevim sončnim celicam zaradi nizke cene in relativno visoke učinkovitosti pretvorbe foton-tok, z nizko porabo energije in enostavnim postopkom procesom proizvodnje izdelave. Tankoplastna sončna celica je sestavljena iz naslednjih komponent: fotoanode, barvila, elektrolita in tokovne elektrode. Tokovna elektroda je ključni element, na kateri se trijodid reducira na jodid z elektroni, ki tečejo skozi zunanji tokokrog. V solarnih celicah je platina najpogosteje uporabljan material za tokovne elektrode zaradi svoje elektrokatalitične aktivnosti (redukcija  $I_3^-$  ionov). Zaradi visoke cene pa uporaba platine vendarle ni optimalna izbira. Torej, da bi dosegli široko uporabo naslednjih generacij fotovoltaike je pomembno razvijati fleksibilne naprave. Članek predstavlja vpliv mehanskih napetosti zaradi upogibanja fleksibilnega substrata na morfologijo in odpornost tokovne elektrode iz ogljikovih nanocev, kot tudi električne lastnosti tankoslojne sončne celice.

Ključne besede: fotovoltaika, tankoslojne barvno občutljive sončne celice, fleksibilni substrati, tokovna elektroda iz ogljikovih nanocev

**1 INTRODUCTION**

The utilisation of renewable energies is of significant importance because of the increase in fossil energy costs in combination with carbon dioxide reduction preventing global warming. The importance of solar energy can be considered as a sustainable energy that may successfully satisfy a part of the energy demand of future generations.<sup>1,2</sup> Photovoltaics seems to be the most promising new electric energy source. What is needed to transform solar power from a marginalised technology to a mainstream source of energy is cheaper materials. At present, the main scientific effort is made to lower the production costs of PV systems and improve their parameters. It is believed that in the not so distant future, thanks to new materials, solar cells could be ubiquitous and one of the cleanest energy sources all over the world.<sup>2,3</sup> There are many publications about the methods of shaping the surface and structure of materials to improve their properties.<sup>4-12</sup> Some materials exhibit a property known as the photovoltaic effect that causes them to absorb photons of

light and excite an electron or other charge carrier to a higher-energy state. When these free electrons are captured, an electric current results that can be used as electricity. In recent years, most of the solar cells are based on a silicon substrate.<sup>11-15</sup> Although the cost per peak watt of crystalline silicon solar cells has significantly dropped, it is still expensive compared to the conventional grid electricity resources.<sup>15</sup>

Dye-sensitized solar cells (DSSCs) are an inexpensive alternative to the conventional p-n junction solar cells. The use of DSSCs is one of the most promising approaches towards the realisation of both high performance and low cost, thanks to their low material cost and ease of manufacturing.<sup>16-18</sup> One of the challenges of this technology is, however, expensive, the heavy and non-elastic glass substrate typically used in DSSCs. Therefore, scientists transfer the DSSC technology from glass substrates to lightweight, cost-efficient, and flexible plastic foils and metal sheets. Additionally, flexible dye-sensitized solar cells built on elastic substrates have

attracted great industrial interest because they can be roll-to-roll printed, which is well suited for scale mass production (accelerate production and reduce cost).<sup>19–21</sup>

In this paper we report on flexible DSSCs based on a carbon-nanotubes counter electrode. The influence of mechanical stress arising from the bending of the flexible substrate on the quality and resistance of the deposited layers was investigated.

A fundamental property of insulators is resistivity. The resistivity can be used to determine the dielectric breakdown, dissipation factor, moisture content, mechanical continuity and other important properties of the material. The volume resistivity of some materials, such as sapphire and Teflon®, can be as high as  $10^{16}$  to  $10^{18}$   $\Omega$ -cm. Because of such large magnitudes, measuring the resistivity of insulators can be difficult unless proper test methods and instrumentation are used. One test method often used for measuring the resistivity of materials is ASTM D-257, "DC Resistance or Conductance of Insulating Materials." Instruments called electrometers are used to make this measurement because of their ability to measure small currents. Two methods are mostly used to measure high resistance, i.e., the constant-voltage method and the constant-current method.<sup>22–23</sup>

In the constant-voltage method, a known voltage is sourced and a picoammeter or electrometer ammeter is used to measure the resulting current. The basic configuration of the constant-voltage method is shown in **Figure 1**. In this method, a constant-voltage source,  $V$ , is placed in series with the unknown resistor,  $R$ , and an electrometer ammeter,  $A$ . Since the voltage drop across an electrometer ammeter is negligible, essentially all the voltage appears across  $R$ . The resulting current is measured by the ammeter and the resistance is calculated using Ohm's law,  $R=V/I$ .<sup>23–24</sup>

In the constant-current method, a constant current is forced through the unknown resistance and the voltage


drop across the resistance is measured. The basic configuration for the constant-current method is shown in **Figure 2**. Current from the constant-current source,  $I$ , flows through the unknown resistance,  $R$ , and the voltage drop is measured by the electrometer voltmeter,  $V$ . Using this method, resistances up to about  $10^{14}$   $\Omega$  can be measured. Even though the basic procedure seems simple enough, some precautionary measures must be taken.<sup>22–24</sup>

One of the components in dye-sensitized solar cells is the counter electrode. The role of the counter electrode is to act as a catalyst for reducing the redox species, which are the mediators for regenerating the sensitizer after the electron injection, or for collecting the hole from the hole-transporting materials.<sup>25–28</sup> This paper presents the influence of mechanical stress arising from the bending of a flexible substrate on morphology, the resistance of the counter electrode based on carbon nanotubes with the addition of poly(3,4-ethylenedioxythiophene)-poly(styrenesulfonate) PEDOT:PSS and polyvinylpyrrolidone PVP as well as electrical properties of dye-sensitized solar cells.


## 2 EXPERIMENTAL PART

Multi-walled carbon nanotubes (MWCNTs) were dispersed in anhydrous ethyl alcohol using ultrasonic dispersion methods. Then the poly(3,4-ethylenedioxythiophene)-poly(styrenesulfonate) PEDOT:PSS was added. Carbon nanotubes are materials that strongly agglomerate. Therefore, they were exposed to dispersion for 45 min. To prevent the aggregation of carbon nanotubes, the mixture of 95 % of mass fractions of active material and 5 % of mass fractions of polyvinylpyrrolidone PVP was used. Using a spin coating methods, the mixture was deposited on the polymer polyethylene terephthalate (PET) with a thin layer of indium tin oxide (ITO) and dried at 60 °C for 25 min. The platinum thin film was deposited on a PET foil in a device based on the sputtering method (Physical Vapour Deposition – PVD) in an Ar atmosphere. The sputtering time was 90 s, the current was 50 mA and the voltage was 50 V.


The photoelectrode was prepared on a flexible ITO-PEN substrate by a doctor-blade technique using a commercially available  $\text{TiO}_2$  nanocrystalline powder P 25 Degussa mixed with ethyl alcohol and distilled water. After that the films were sintered at 120 °C for 4 h. The photoelectrodes were immersed in the anhydrous ethanol solution of 0.5-mM N3 (Cis-diisothiocyanato-bis(2,2'-bipyridyl-4,4'-dicarboxylic acid) ruthenium(II), Solaronix) for 24 h at room temperature. The internal space between the photoanode and the counter electrode was controlled at 25  $\mu\text{m}$  by Surlyn foil (Solaronix). The photoanode and counter electrode were sealed with a 25- $\mu\text{m}$ -thick Surlyn frame at 100 °C for 15 s. After sealing the cells were filled with the electrolyte solution

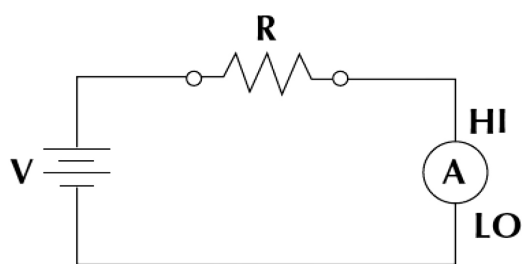

**Figure 1:** The constant-voltage method for measuring resistance<sup>22–24</sup>

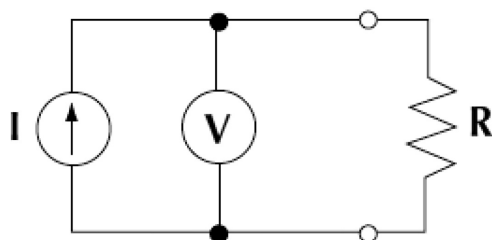

**Figure 2:** The constant-current method for measuring resistance<sup>22–24</sup>

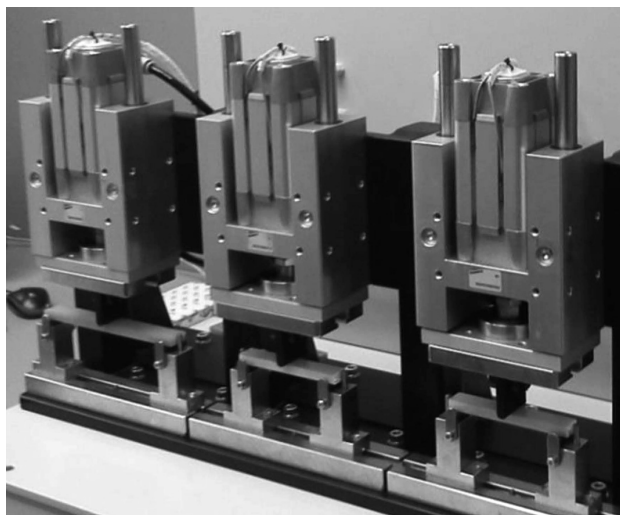


**Figure 3:** Tester for measuring the bending strength of polymeric materials

with redox couple  $I^-/I_3^-$  through the hole in a counter electrode.


The influence of the mechanical stress arising from the bending of the flexible substrate on the quality and resistance of counter electrode based on carbon nanotubes with the addition of PEDOT:PSS and PVP. The samples were bent with the tester for measuring the bending strength of polymeric materials (**Figure 3**).

The morphology of the counter electrodes based on platinum and carbon nanotubes deposited on a PET foil was performed using a scanning electron microscope (Zeiss Supra 35). In order to obtain images of the surface topography, the detection of secondary electrons by the detector In Lens was used.

The resistance of the prepared samples was measured using a Keithley meter. The meter was connected to a specialised adapter for testing thin films. This was in

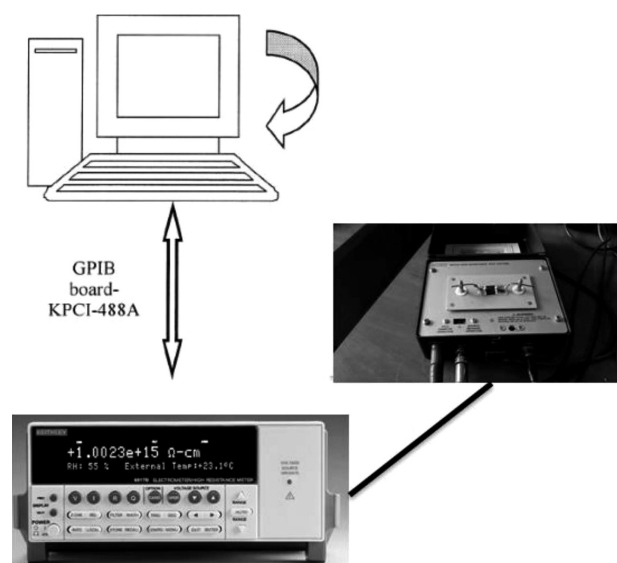

**Figure 4:** General measurement system set-up

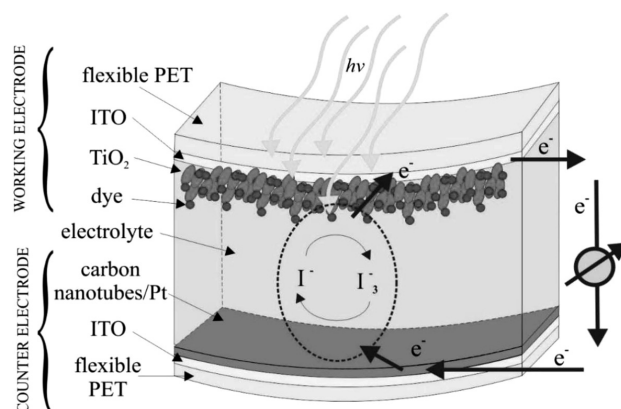

**Figure 5:** Construction of dye-sensitized solar cell

order to better contact and more accurately measure on the edge of the layers applied silver contacts connected to external electrodes. The measurement block diagram used for our measurements is presented in **Figure 4**.

Resistance measurements were made using a constant-voltage measurement in real time with the current running. The chosen method allows us to obtain reliable results only for layers deposited on a polymer foil. It can be assumed that the resistance of the layers is the same or similar, regardless of the substrate.

Electrical parameters of manufactured flexible dye-sensitized solar cells with a counter electrode based on platinum and carbon nanotubes with the addition of PEDOT:PSS and PEDOT:PSS/PVP were characterised by measurements of I-V illuminated characteristics on PV Test Solutions Tadeusz Żdanowicz Solar Cell I-V Tracer System under standard test condition (AM 1.5, 1000W/m<sup>2</sup>). The level of irradiance was determined using the reference cells with a KG5 filter.

The construction of flexible dye-sensitized solar cells is illustrated in **Figure 5**.

The structure of produced DSSCs consists of components:

- working electrode – dye molecule (N3) coated nanocrystalline porous TiO<sub>2</sub> deposited on PET/ITO substrate,
- counter electrode – carbon nanotubes with the addition of PEDOT:PSS and PVP deposited on PET/ITO substrate,
- electrolyte (Iodolyte Z-150, Solaronix) containing an I<sup>-</sup>/I<sub>3</sub><sup>-</sup> redox couple.

### 3 RESULTS AND DISCUSSION

**Figure 6** shows the morphology of the PET/ITO foil coated with the Pt film. It illustrates that the substrate is uniformly covered with the Pt film.

A detailed inspection of scanning electron microscope micrographs of PET/ITO foils coated with the Pt film after bending revealed microcracks and crevices (**Figure 7**). This indirectly indicates that platinum film



A. DRYGAŁA et al.: A CARBON-NANOTUBES COUNTER ELECTRODE FOR FLEXIBLE DYE-SENSITIZED SOLAR CELLS

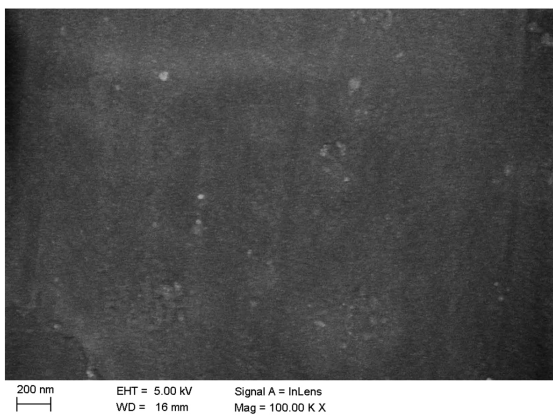


Figure 6: SEM images of platinum on PET/ITO foil

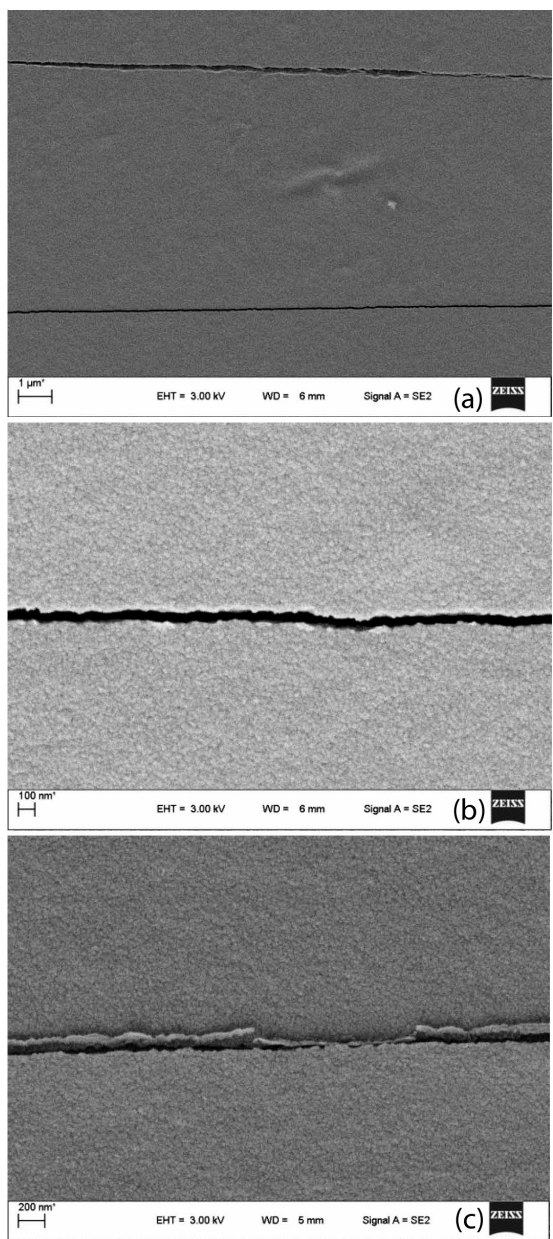


Figure 7: SEM images of platinum on PET/ITO foil after 100 bending cycles

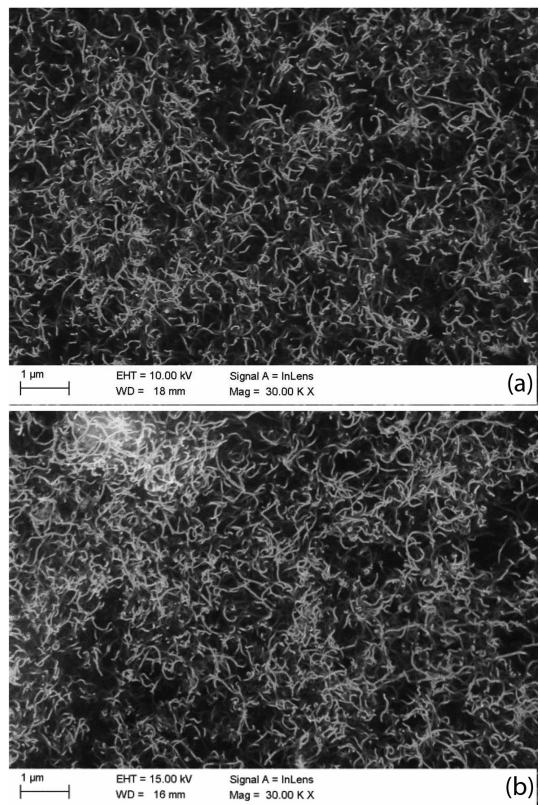


Figure 8: SEM images of counter electrode based on carbon nanotubes with addition: a) PEDOT:PSS/PVP, b) PEDOT:PSS after 100 bending cycles

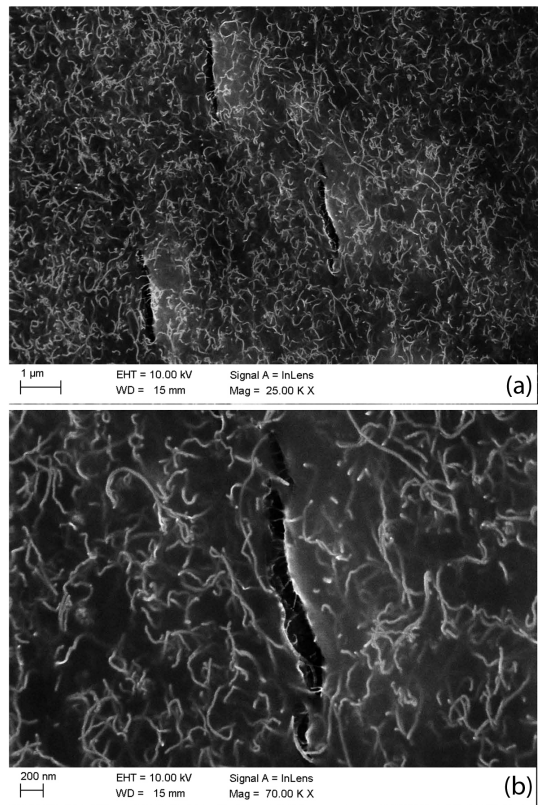


Figure 9: SEM images of counter electrode based on carbon nanotubes with addition PEDOT:PSS/PVP after 100 bending cycles

can have poor properties for catalytic activity at the counter electrode and electrical conductivity for the charge transfer. The cracks are formed mainly along the bending line. Moreover, the PET foil coated with ITO and Pt after 100 bending cycles in some places delaminates and breaks away from the elastic substrate (Figure 7).

Figure 8 shows the SEM images of a counter electrode based on carbon nanotubes with the addition of PEDOT:PSS and PEDOT:PSS/PVP. The addition of 5 % of mass fractions of polyvinylpyrrolidone PVP prevents the agglomeration of carbon nanotubes. It was observed that, after the same number of bending cycles, the surface of the counter electrode based on carbon nanotube with the addition of PEDOT:PSS/PVP is much more damaged than the surface of the counter electrode without PVP (Figures 9 and 10). However, the amount of damage and the size of the defects in the carbon-nanotubes counter electrode is much smaller than in the platinum foil. It can be seen that carbon nano-elements reduce the spread of cracks.

The resistance of the carbon-nanotubes thin films with the addition of the PEDOT:PSS polymer was about  $4 \cdot 10^3 \Omega$  (Figure 11). The appearance of small cracks registered using a scanning electron microscope did not affect significantly the results of electrical measurements. Mechanical stress caused by the bending of the substrate slightly affected the resistance of the tested

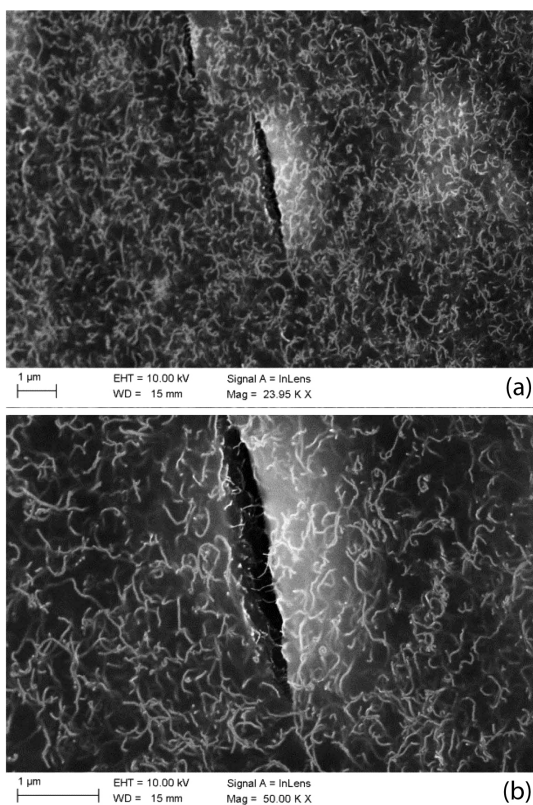


Figure 10: SEM images of counter electrode based on carbon nanotubes with addition PEDOT:PSS after 100 bending cycles

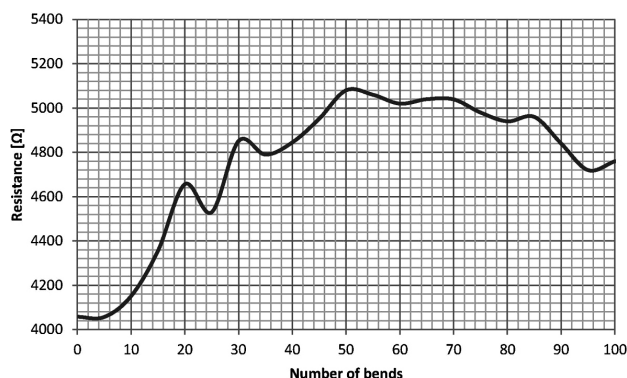


Figure 11: Influence of mechanical stress on the resistance of carbon-nanotubes thin films with the addition of PEDOT:PSS deposited on a PET foil

layer. After 50 cycles of the bending, the resistance value increased to about  $5.08 \cdot 10^3$ . Further bending does not result in significant changes in resistance and maintained at the similar level.

The addition of PVP polymer, which prevents agglomeration, caused a significant deterioration of the resistance to about  $7 \cdot 10^{10} \Omega$  (Figure 12). The results of the electrical properties measurement are correlated with the surface studies conducted on a scanning electron microscope. The impact of mechanical stress increased. The appearance of micro-cracks after 100 cycles of bending of the substrate increased the resistance to about  $1.6 \cdot 10^{11} \Omega$ . Therefore, registered increases the resistance by more than one order of magnitude.

Table 1: Conversion efficiency of dye-sensitized solar cells with counter electrodes based on platinum and carbon nanotubes with the addition of PEDOT:PSS and PEDOT:PSS/PVP

Number of bending cycles	Type of counter electrode		
	Platinum	Carbon nanotubes with the addition of PEDOT:PSS/PVP	Carbon nanotubes with the addition of PEDOT:PSS
0	4.02 %	3.61 %	3.42 %
100	2.42 %	2.65 %	2.96 %

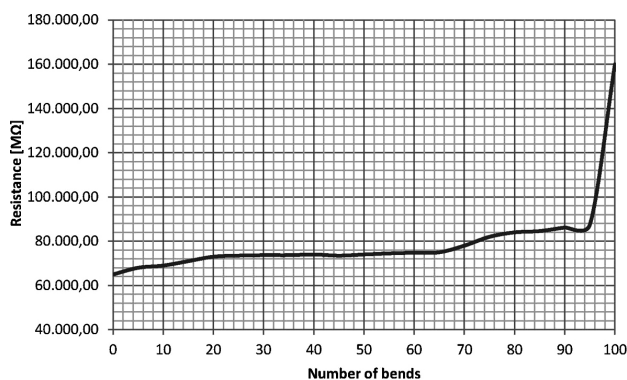


Figure 12: Influence of mechanical stress on the resistance of carbon-nanotubes thin films with the addition of PEDOT:PSS and PVP deposited on a PET foil



The efficiency of dye-sensitized solar cells with different types of counter electrodes is presented in Table 1. These results indicate that the photovoltaic properties of dye-sensitized solar cells after bending is decreased. Platinum is a preferred material for the counter electrode because of its high conductivity and catalytic activity. However, dye-sensitized solar cells based on a platinum counter electrode subjected to the impact of mechanical stress demonstrate the lowest efficiency. This is the result of damage introduced into the platinum thin film deposited by a sputtering method and its delamination from the flexible substrate (**Figure 7**). These damages have a detrimental influence on the proper working of the solar cell and reduce its properties, which could be a consequence of poorer charge transfer. It can be observed that the carbon-nanotubes counter electrode is more resistant to bending compared to the platinum counter electrode.

#### 4 CONCLUSION

Flexible dye-sensitized solar cells built on elastic substrates have attracted great interest as they are light-weight and can be roll-to-roll printed to accelerate production and reduce costs. The study showed the possibility of replacing the standard platinum counter electrode by carbon nanotubes deposited on the elastic substrate. In the frame of this work, we investigated the influence of mechanical stress arising from the bending of a flexible substrate on the morphology, the resistance of the counter electrode based on carbon nanotubes as well as the electrical properties of dye-sensitized solar cells.

It was found that the bending has a significant influence on the morphology of platinum layer deposited on a PET foil. It was shown that on the platinum surface after bending cracks were formed and in some places the layer was delaminated and broken away from the substrate. The addition of PVP to the counter electrode based on carbon nanomaterials with PEDOT:PSS prevents agglomeration of carbon nanotubes, but after a bending test the resistivity of the prepared layer and electrical properties of produced dye-sensitized solar cells are reduced. The amount of damage and the size of defects in the carbon nanotubes counter electrode is much smaller than in the platinum foil. Moreover, it can be seen that carbon nano-elements reduce the spread of cracks. Mechanical stress slightly effects the resistance of studied carbon nanotubes layers with the addition of PEDOT:PSS. Only the addition of the PVP polymer, which prevents agglomeration, caused a significant deterioration of the resistance as well as the increased influence of mechanical stress. These damages have a detrimental influence on the operation of solar cells and reduce their efficiency.

#### Acknowledgements

The project was funded by the National Science Centre on the basis of the contract No. DEC-2013/09/B/ST8/02943. This publication was co-financed by the Ministry of Science and Higher Education of Poland as the statutory financial grant of the Faculty of Mechanical Engineering SUT.

#### 5 REFERENCES

- J. Jarman, E. Khalil, E. Khalaf, Energy Analyses of Thermoelectric Renewable Energy Sources. *Open Journal of Energy Efficiency*, 2 (2013), 143–153 doi:10.4236/ojee.2013.24019
- S. Al-Hallaj, K. Kiszynski, Renewable Energy Sources and Energy Conversion Devices, Green Energy and Technology, Springer-Verlag London, (2011) 9–29, doi:10.1007/978-1-84628-467-0\_2
- V. V. Tyagi, Nurul A. A. Rahim, N. A. Rahim, J. A. L. Selvaraj, Progress in solar PV technology: Research and achievement, Renewable and Sustainable Energy Reviews 20 (2013), 443–461, doi:10.1016/j.rser.2012.09.028
- L. A. Dobrzański, T. Tański, A. Dobrzańska-Danikiewicz, E. Jonda, M. Bonek, A. Drygała, Structures, properties and development trends of laser-surface-treated hot-work steels, light metal alloys and polycrystalline silicon, Laser surface engineering. Processes and applications, Book Series: Woodhead Publishing Series in Electronic and Optical Materials, 65 (2015), 3–32, doi:10.1016/B978-1-78242-074-3.00001-5
- S. Lesz, R. Szewczyk, D. Szewieczek, A. Bieńkowski: The structure and magnetoelastic properties of the Fe-based amorphous alloy with Hf addition, *Journal of Materials Processing Technology*, 157–158 (2004), 743–748, doi:10.1016/j.jmatprotec.2004.07.133
- K. Drabczyk, G. Kulesza-Matlak, A. Drygała, M. Szindler, M. Lipiński, Electroluminescence imaging to determining the influence of metallization parameters for solar cells metallic contacts, *Solar Energy*, 126 (2016), 14–21, doi:10.1016/j.solener.2015.12.029
- A. Zieliński, G. Golański, M. Sroka: Influence of long-term ageing on the microstructure and mechanical properties of T24 steel, *Materials Science & Engineering A*, 682 (2017), 664–672. doi:10.1016/j.msea.2016.11.087
- A. Zieliński, M. Sroka, M. Miczka, A. Śliwa: Forecasting the particle diameter size distribution in P92 (X10CRWMOVNB9-2) steel after long-term ageing at 600 and 650 °C, *Archives of Metallurgy and Materials*, 61 2A (2016), 753–760, doi:10.1515/amm-2016-0128
- K. Drabczyk, P. Panek, Influence of screen printing parameters on the front metallic electrodes geometry of solar cells, *Circuit World*, 40 (2014) 1, 23–26, doi:10.1108/CW-10-2013-0038
- L. A. Dobrzański, K. Lukaszewicz, Erosion resistant and tribological properties of coatings deposited by reactive magnetron sputtering method onto the brass substrate, *Journal of Materials Processing Technology* 157-158 (2004), 317–323, doi:10.1016/j.jmatprotec.2004.09.050
- A. Drygała, L. A. Dobrzański, M. Szindler, M. M. Szindler, M. Prokopiuk vel Prokopowicz, E. Jonda, Influence of laser texturization surface and atomic layer deposition on optical properties of polycrystalline silicon, *International Journal of Hydrogen Energy*, 41 (2016) 18, 7563–7567, doi:10.1016/j.ijhydene.2015.12.180
- L. A. Dobrzański, A. Drygała, Influence of laser processing on polycrystalline silicon surface, *Materials Science Forum*, 706–709 (2012), 829–834, doi:10.4028/www.scientific.net/MSF.706-709.829
- K. Drabczyk, R. Socha, P. Panek, G. Mordarski, Electrodeposition of thin metallic layer for solar cell electrodes, *Soldering & Surface Mount Technology*, 26(1) (2014), 18–21, doi:10.1108/SSMT-10-2013-0032

A. DRYGAŁA et al.: A CARBON-NANOTUBES COUNTER ELECTRODE FOR FLEXIBLE DYE-SENSITIZED SOLAR CELLS

- <sup>14</sup> C. Battaglia, A. Cuevas and S. De Wolf, High-efficiency crystalline silicon solar cells: status and perspectives, *Energy & Environmental Science*, 9 (2016), 1552–1576, doi:10.1039/C5EE03380B
- <sup>15</sup> S. Sharma, K. K. Jain, A. Sharma, Solar cells: in research and applications – a review, *Materials Sciences and Applications*, 6 (2015), 1145–1155, doi:10.4236/msa.2015.612113
- <sup>16</sup> J. Gong, J. Liang, K. Sumathy, Review on dye-sensitized solar cells (DSSCs): Fundamental concepts and novel materials, *Renewable and Sustainable Energy Reviews*, 16 (2012), 5848–5860, doi:10.1016/j.rser.2012.04.044
- <sup>17</sup> M. Berginc, M. Topic, U. O. Krasovec, Recovery of dye-sensitized solar cell's performance by heat treatment, *Physical Chemistry Chemical Physics*, 16 (2014), 12940–12948, doi:10.1039/C4CP01463D
- <sup>18</sup> L. A. Dobrzański, M. M. Szindler, M. Szindler, K. Lukaszewicz K., A. Drygała, M. Prokopiuk vel Prokopowicz, Nanocrystalline TiO<sub>2</sub> powder prepared by sol-gel method for dye-sensitized solar cells, *Archives of Metallurgy and Materials*, 61(2) (2016), 833–836, doi:10.1515/amm-2016-0140
- <sup>19</sup> H. C. Weerasinghe, F. Huang, Y. Cheng, Fabrication of flexible dye sensitized solar cells on plastic substrates, *Nano Energy*, 2 (2013) 2, 174–189, doi:10.1016/j.nanoen.2012.10.004
- <sup>20</sup> G. Yue, X. Ma, W. Zhang, F. Li, J. Wu, G. Li, A highly efficient flexible dye-sensitized solar cell based on nickel sulfide/platinum/titanium counter electrode, *Nanoscale Res Lett.* 10 (2015) 1, doi:10.1186/1556-276X-10-1
- <sup>21</sup> Y. Han, J. M. Pringle, Y. Cheng, Photovoltaic characteristics and stability of flexible dye-sensitized solar cells on ITO/PEN substrates, *RSC Advances*, 4 (2014), 1393–1400, doi:10.1039/C3RA45508D
- <sup>22</sup> [http://www-eng.lbl.gov/~shuman/NEXT/CURRENT\\_DESIGN/TP/MATERIALS/ASTM-D257\\_resistance\\_meas.pdf/](http://www-eng.lbl.gov/~shuman/NEXT/CURRENT_DESIGN/TP/MATERIALS/ASTM-D257_resistance_meas.pdf/), 30.06.2016
- <sup>23</sup> <http://www.electrotechsystems.com/manuals/2-%20PDF%20Electrostatic%20Manuals/853%20Manual%20Rev1%209-10.pdf/>, 30.06.2016
- <sup>24</sup> <https://www.ipc.org/TM/2-6-3-7.pdf/>, 30.06.2016
- <sup>25</sup> S. Thomas, T. G. Deepak, G. S. Anjusree, T. A. Arun, Shantikumar V. Nair, A. Sreekumaran Nair, A review on counter electrode materials in dye-sensitized solar cells, *Journal of Materials Chemistry A*, 2 (2014), 4474–4490, doi:10.1039/C3TA13374E
- <sup>26</sup> A. Drygała, L. A. Dobrzański, M. Szindler, M. Prokopiuk vel Prokopowicz, M. Pawlyta, K. Lukaszewicz, Carbon nanotubes counter electrode for dye-sensitized solar cells application, *Archives of Metallurgy and Materials* 61 (2016) 2, 803–80, doi:10.1515/amm-2016-0135
- <sup>27</sup> L. A. Dobrzański, A. Mucha, M. Prokopiuk vel Prokopowicz, M. Szindler, A. Drygała, K. Lukaszewicz, Characteristics of dye-sensitized solar cells with carbon nanomaterials, *Mater. Tehnol.*, 50 (2016) 5, 649–654, doi:10.17222/mit.2014.134
- <sup>28</sup> I. Y. Bu, J. Zheng, A new type of counter electrode for dye sensitized solar cells based on solution processed SnO<sub>2</sub> and activated carbon, *Materials Science in Semiconductor Processing*, 39 (2015), 223–228, doi:10.1016/j.mssp.2015.04.029